

EFFECT OF METAL OXIDE NANOPARTICLE ON CURING KINETIC OF BIORESIN

WAN NURUL NAJIHAH BINTI WAN GHAFAR

Thesis submitted in partial fulfilment of the requirements
for the award of the degree of
Bachelor of Chemical Engineering

**Faculty of Chemical & Natural Resources Engineering
UNIVERSITI MALAYSIA PAHANG**

JUN 2015

©WAN NURUL NAJIHAH BINTI WAN GHAFAR (2015)

ABSTRACT

Development of polymers from renewable resources have received great scientific attention. Amongst different renewable resources, plant oils have attracted much attention as raw materials for chemical industry. Vegetable oils have been utilized in the synthesis of various polymeric resin such as alkyd resins and polyester. Alkyd resins find an extensive applications in surface-coating, adhesive and composite materials. Alkyd resins were blended with other suitable resins to overcome problems such as low mechanical strength, low hardness, low thermal stability, and long curing time. Polymer nanocomposite based on nanoparticles such as metal oxide are being developed. Nanoparticles are reported to have strong impact on thermal, mechanical, electrical barrier, and flame retardant properties on nanocomposite. In the present study, alkyd resin was prepared from the vegetable oil (ratio of Palm oil to Jatropha oil at 1:1) via two stage method (alcoholysis-polyesterification). The alkyd resin was mixed with commercial epoxy resin to form a blend mixture. Apart from that, zinc oxide (ZnO) nanoparticle was mechanically mixed with the blend to form alkyd-epoxy-ZnO. Prior to that, ZnO was synthesized using a simple precipitation method. The as-prepared ZnO was characterized by X-ray diffraction (XRD) and the crystallite size was calculated by using Debye-Scherrer's equation. Scanning electron microscopy (SEM) was used to characterize the morphologies of the sample. The curing kinetic of alkyd-epoxy-ZnO blend was investigated by using non-isothermal differential scanning calorimetry (DSC) method. The effect of alkyd/epoxy ratio and ZnO nanoparticle loading on curing enthalpy was investigated. From DSC results, the peak temperature, T_p is used to calculate the activation energy, E_a by using Kissinger and Ozawa method. In addition, thermogravimetric analysis (TGA) was carried out to study the thermal degradation of the nanocomposites. The interaction between ZnO nanoparticles and the alkyd/epoxy blend were recorded by Fourier-transform infrared (FTIR). All the results from the analysis deduce a conclusion that the ZnO nanoparticles have significant effects on the performance characteristics of alkyd/epoxy blends.

ABSTRAK

Pembangunan polimer daripada sumber yang boleh diperbaharui telah mendapat perhatian saintifik yang besar. Di antara sumber yang boleh diperbaharui, minyak tumbuhan telah menarik perhatian sebagai bahan mentah untuk industri kimia. Minyak sayuran telah digunakan dalam sintesis pelbagai resin polimer seperti resin alkyd dan poliester. Resin alkyd mempunyai aplikasi yang luas dalam permukaan salutan, pelekat dan bahan komposit. Resin alkyd telah dicampur dengan resin lain yang sesuai untuk mengatasi masalah seperti kekuatan mekanikal rendah, kekerasan rendah, kestabilan haba yang rendah, dan masa pengawetan panjang. Polimer nanokomposit berdasarkan nanopartikel seperti oksida logam sedang dibangunkan. Nanopartikel dilaporkan mempunyai kesan yang kuat terhadap haba, mekanikal, elektrik halangan, dan sifat-sifat kalis api pada nanokomposit. Dalam kajian ini, resin alkyd telah disediakan daripada minyak sayuran (nisbah minyak sawit kepada minyak *Jatropha*; 1: 1) melalui dua kaedah peringkat (alkoholisis-polyesterification). Resin alkyd dicampur-campur dengan resin epoksi komersil untuk membentuk campuran gabungan. Selain itu, zink oksida (ZnO) nanopartikel dicampur dengan campuran untuk membentuk alkyd-epoxy-ZnO. Sebelum itu, ZnO telah disintesis dengan menggunakan kaedah pemendakan mudah. ZnO yang disediakan telah dicirikan oleh pembelauan sinar-X (XRD) dan saiz kristalnya dikira dengan menggunakan persamaan Debye-Scherrer. Mikroskop imbasan elektron (SEM) telah digunakan untuk ciri-ciri morfologi sampel. Kinetik menyembuhkan campuran alkyd-epoxy-ZnO disiasat dengan menggunakan kaedah bukan suhu kalorimeter pengimbasan perbezaan (DSC). Kesan nisbah alkyd / epoksi dan ZnO nanopartikel pada menyembuhkan entalpi dikaji. Dari keputusan DSC, suhu puncak, T_p digunakan untuk mengira tenaga pengaktifan, E_a dengan menggunakan kaedah Kissinger dan Ozawa. Di samping itu, analisis Termogravimetri (TGA) telah dijalankan untuk mengkaji degradasi terma nanokomposit. Interaksi antara partikel nano ZnO dan gabungan alkyd / epoksi telah direkodkan oleh Fourier-mengubah inframerah (FTIR). Semua keputusan daripada analisis disimpulkan bahawa nanopartikel ZnO mempunyai kesan yang besar ke atas ciri-ciri prestasi campuran alkyd / epoksi.

TABLE OF CONTENTS

SUPERVISOR'S DECLARATION	IV
STUDENT'S DECLARATION	V
<i>Dedication</i>	VI
ACKNOWLEDGEMENT	VII
ABSTRACT.....	VIII
ABSTRAK.....	IX
TABLE OF CONTENTS.....	IX
LIST OF FIGURES	XII
LIST OF TABLES.....	XIII
LIST OF ABBREVIATIONS.....	XIV
1 INTRODUCTION	1
1.1 Background, motivation and statement of problem	1
1.2 Objectives.....	3
1.3 Scope of this research.....	3
1.4 Organisation of this thesis	3
2 LITERATURE REVIEW	5
2.1 Overview	5
2.2 Preparation of alkyd resins from vegetable oils	5
2.3 Blending of oil modified alkyd resin with the synthetic resin	8
2.4 Curing behaviour of the resins	10
2.4.1 Curing of the blend	10
2.4.2 Effect of nanoparticle on curing	11
2.5 Summary	13
3 MATERIALS AND METHODS.....	14
3.1 Overview	14
3.2 Materials.....	14
3.3 Synthesis of Zinc Oxide (ZnO) nanoparticle	14
3.4 Synthesis of alkyd resin from the oil blend.....	15
3.5 Preparation of the Alkyd/Epoxy Resin and Alkyd/Epoxy/ZnO nanocomposite	16
3.6 Characterization techniques	18
3.6.1 X-ray diffractometer (XRD)	18
3.6.2 Scanning electron microscopy (SEM)	18
3.6.3 Differential scanning calorimeter (DSC)	18
3.6.4 Fourier-transform infrared (FTIR) spectra	18
3.6.5 Thermogravimetric analysis (TGA).....	18
3.7 Kinetic analysis	19
4 RESULTS AND DISCUSSIONS.....	21
4.1 ZnO nanoparticle preparation and characterization by XRD.....	21
4.2 SEM and EDS analysis	23
4.3 Preparation of alkyd resin	24
4.4 Characterization of alkyd resin using DSC.....	25
4.5 FTIR spectroscopic analysis of alkyd/epoxy blend	26
4.6 TGA study of alkyd/epoxy blend by incorporation of ZnO.....	28
4.7 Blending of alkyd/epoxy resin	29

4.8	Effect of ZnO nanoparticle on alkyd resin	31
4.9	Preparation of nanocomposite by incorporation of ZnO.....	32
4.10	Non-isothermal DSC of alkyd/epoxy/ZnO blend at various heating rates ...	33
4.11	Kinetic model	34
5	CONCLUSION.....	36
5.1	Conclusion.....	36
5.2	Future work	36
	REFERENCES	37
	APPENDICES	41

LIST OF FIGURES

Figure 2-1 DSC traces of (a) alkyd/epoxy blend, (b) nanocomposite (1% NiO), (c) nanocomposite (2% NiO), (d) nanocomposite (3% NiO).	12
Figure 4-1 XRD patterns of ZnO calcined at different temperatures	21
Figure 4-2 SEM images of ZnO samples calcined at three different temperatures.	23
Figure 4-3 Energy dispersive spectra (EDS) of ZnO calcined at 700 °C	23
Figure 4-4 Graph of acid value for alkyd resin.....	24
Figure 4-5 DSC thermograms of palm oil alkyd and blending of jatropha with palm oil alkyd.....	25
Figure 4-6 FTIR spectra of epoxy neat and alkyd/epoxy blend	26
Figure 4-7 TGA thermograms of alkyd/epoxy blend and alkyd/epoxy/ZnO nanocomposite	28
Figure 4-8 Dynamic DSC thermograms of alkyd/epoxy blend at different ratio of epoxy/alkyd obtained at scanning rate of 10°C/min.....	29
Figure 4-9 Dynamic DSC thermograms of alkyd/ZnO blend at different weight % of ZnO nanoparticle obtained at scanning rate of 10°C/min.....	31
Figure 4-10 Dynamic DSC thermograms of alkyd/epoxy/ZnO nanocomposite blend at different weight % of ZnO nanoparticle obtained at scanning rate of 10°C/min	32
Figure 4-11 DSC curves of 40:60 alkyd/epoxy blend cured with 1wt % ZnO nanoparticle at different heating rate of 10, 15, 20 and 25 °C/min.....	33
Figure 4-12 Kissinger method is applied to DSC exotherm for determination Ea.....	34
Figure 4-13 Ozawa method is applied to DSC exotherm for determination Ea	35

LIST OF TABLES

Table 2-1 Fatty acid composition %	6
Table 2-2 Property of alkyd resin blended with different percentages of palm oil	9
Table 2-3 The result of DSC measurements of DGEBA/DABN at different level of ZnO nanoparticles at heating rate 10 K/min	11
Table 2-4 Mechanical properties of the nanocomposite	12
Table 3-1: Composition of the ingredients to produce alkyd resins	15
Table 3-2 Different ratio by mass of alkyd to epoxy resin	16
Table 3-3 Different wt % of ZnO nanoparticle.....	17
Table 4-1 Crystallite size of ZnO obtained from XRD	22
Table 4-2 Results of DSC measurements of different ratio of alkyd/epoxy.....	30
Table 4-3 Results of DSC measurements of alkyd at different weight percentage of nano ZnO	31
Table 4-4 Results of DSC measurements of alkyd/epoxy at different weight percentage of nano ZnO	32
Table 4-5 Data from the analysis of DSC measurements at different heating rate	33

LIST OF ABBREVIATIONS

DSC	Differential scanning calorimetry
EDS	Energy dispersive spectra
EJO	Epoxidised jatropha oil
FTIR	Fourier-transform infrared
MEKP	Methyl ethyl ketone peroxide
SEM	Scanning electron microscopy
TGA	Thermogravimetric analysis
XRD	X-ray diffractometer

1 INTRODUCTION

1.1 Background, motivation and statement of problem

Sustainable economic growth needs guaranteed sources of raw materials for the industrial production. Nowadays, petroleum, a non-renewable resource is the most important source of industrial chemicals. As petroleum sources are being exhausted and causes environmental pollutions, there is a growing effort to make biomass as an alternative source of raw materials for sustainable growth. Polymers are an important class of industrial product and are mainly been synthesized from petroleum based raw materials which need to be replaced by the bio-based raw materials to make it sustainable. One of the industrial polymers is alkyd resin which is also known as bioresin. Bioresin is a polyester comprising of one or more reacted di-acid monomer units and one or more reacted diol monomer units where at least one of the reacted di-acid monomer units or at least one of the reacted diol monomer units is a bio-monomer obtained from a plant or an animal source (Urban & Owada, 2012). Alkyd resins are formed from the polymeric condensation of polyhydric alcohols, polybasic acids and monobasic fatty acids. Alkyds are used in the formulation of paints, varnishes, lacquers and other finishes, which make alkyd resins as a necessary raw material (Odetoye T. O., 2012). Alkyd resins are used in surface coating and composite formation due to their good characteristic such as strength, flexibility, gloss retention, good thermal stability and low price (Ling, 2014).

Oil is one of the important raw materials used in the production of oil modified alkyd resins. Vegetable oils are commonly and widely used in the manufacture of oil modified alkyd resins. Alkyd resin can be synthesized from both edible and non-edible vegetable oil sources. Non-edible oil is preferred to be used as an alternative source to synthesis alkyd resin due to its lack of food value. Among non-edible oils, jatropha (Kumar, Yaakob, Maimunah, Siddaramaiah, & Abdullah, 2010), nahar (Dutta, 2004), yellow oleander (Deka. D.C., 2011) and karanja (*Millettia pinnata*) (Bora, Deka, Ahmed, & Kakati, 2014) oil are been investigated as potential source for the preparation of oil modified alkyd resin. Alkyd resin can significantly reduce or remove the risk associated with cross-linking agents used in other resin systems, such as sulphur in furan based resins. By using plant oils, it can create polymers with a greater intra-chain

length compared to the traditional resins. On curing, this property produces a structure that can be less brittle (providing flexibility before mechanical failure) allowing for improved impact resistance in structural applications.

Malaysia is rich in palm oil production, which known as non-drying oil due to the presence of low degree of unsaturation. Unsaturated oils are been preferred to produce bioresin due to the higher degree of cross-linking through the double bonds. Jatropha oil is one of the promising raw materials for bioresin synthesis, as it contains a high percentage of monounsaturated oleic (44.7%) and polyunsaturated linoleic acids (32.8%) (E., Z., S.K., M., & J., 2009) indicating a semi-drying property (Odetoeye T. O., 2012). To the authors knowledge, there is no study reported the blending of palm oil with jatropha oil to produce bioresin. However, the blending of non-drying oil with semi-drying oil might increase the curing rate of the non-drying oil.

Furthermore, in recent years, metal nanoparticles are extensively studied to enhance the properties of the nanocomposites made from the bioresin. Pronob et al. reported the use of NiO nanoparticle on the properties of Jatropha oil based alkyd resin and epoxy blend, where the incorporation of the nanoparticle reduced the mobility of the polymer chain and increased the mechanical properties by many times. Zinc oxide nanoparticle, a multifunctional inorganic material, has drawn attention in recent years due to its outstanding physical and chemical properties, such as chemical stability, low dielectric constant, high luminous transmittance, high catalyst activity, effective antibacterial and bactericide, intensive ultraviolet and infrared absorption. Moreover, the incorporation of ZnO nanoparticles could improve the mechanical and optical properties of the polymer matrix (Omid, et al., 2011). However, the curing behaviour of the alkyd resin or the resin blends by incorporation of the metal oxide nanoparticles are not reported well throughout the literature. Hence in the present study attempts were made to prepare bioresin from jatropha and palm oil blend (1/1 wt % ratio) and the effect of ZnO nanoparticle on the curing behaviour of the composite have been investigated. Furthermore, bioresin/epoxy blend and its curing behaviour with and without ZnO nanoparticle have been studied.

1.2 Objectives

The following are the objective of this research:

- To study the effect of zinc oxide nanoparticle on the curing kinetic of bioresin.

1.3 Scope of this research

The following are the scope of this research:

- i) To synthesized nanoparticles through sol gel method. The prepared nanoparticle was applied as catalysts during curing process.
- ii) To synthesized bioresin by using two stages of alcoholysis-polyesterification method by mixing palm oil, jatropha oil, glycerol and phthalic anhydride.
- iii) To prepared nanocomposite by mixing bioresin and nanoparticles via ultrasonic method. The curing kinetics of nanocomposite was investigated by using DSC method and its durability is checked by antimicrobial test.

1.4 Organisation of this thesis

The structure of the reminder of the thesis is outlined as follow:

Chapter 2 provides a description of preparation method of alkyd resin from various type of non-edible vegetable oil such as yellow oleander (*Thevetia peruviana*), karanja (*Millettia pinnata* (L.) Panigrahi) and jatropha *curcas* Linneaus. Fatty acid composition of Jatropha curcas oil seed, palm kernel oil, sunflower oil, soybean oil and palm oil was compared. Blending of oil modified alkyd resin with synthetic resin such as epoxy, acrylic and melamine was observed. The preparation and characterization of blends of alkyd resin and palm oil also been studied. Various physico-chemical properties such as density, viscosity, drying time, acid value, peroxide value and dry extract are observed. The effect of zinc oxide (ZnO) nanoparticle on the thermal degradation kinetics and mechanical properties of epoxy resin and nickel oxide (NiO) nanoparticles on the performance characteristics of the Jatropha oil based alkyd and epoxy blends have been reported. The curing behaviour of the resin was analysed by differential scanning calorimeter (DSC).

Chapter 3 gives a review on the process to study the effect of zinc oxide nanoparticles on curing kinetic of alkyd resins. The process starts from the synthesis of zinc oxide

nanoparticles by using sol-gel method, synthesis of alkyd resin from vegetable oil by using two stages alcoholysis-polysterification and preparation of alkyd/epoxy blend and alkyd/epoxy/ZnO nanocomposite by mechanical blending method. The structure and morphologies of ZnO nanoparticles was characterized by x-ray diffraction (XRD) and scanning electron microscopy (SEM) while the blending alkyd and the nanocomposite was characterized by differential scanning calorimeter (DSC), fourier transform infrared (FTIR) spectra and thermogravimetric analysis (TGA).

Chapter 4 discuss on the result obtained from the analysis of x-ray diffraction (XRD), scanning electron microscopy (SEM), differential scanning calorimeter (DSC), fourier transform infrared (FTIR) spectra and thermogravimetric analysis (TGA). The effect of alkyd/epoxy ratio and ZnO nanoparticle loading on curing enthalpy was investigated. From DSC results, the peak temperature, T_p is used to calculate the activation energy, E_a by using Kissinger and Ozawa method.

Chapter 5 draws together a summary of the thesis and outlines the future work which might be derived from the model developed in this work.

2 LITERATURE REVIEW

2.1 Overview

This chapter presents the preparation method of alkyd resin from various type of non-edible vegetable oil. Fatty acid composition of jatropha curcas oil seed, palm kernel oil, sunflower oil, soybean oil and palm oil was compared. The preparation and characterization of blends of alkyd resin with synthetic resin and palm oil also been studied. Various physico-chemical properties such as density, viscosity, drying time, acid value, peroxide value and dry extract are observed. The effect of zinc oxide (ZnO) nanoparticle on the thermal degradation kinetics and mechanical properties of epoxy resin and nickel oxide (NiO) nanoparticles on the performance characteristics of the Jatropha oil based alkyd and epoxy blends was reported. The curing kinetic of the blend was studied by using DSC.

2.2 Preparation of alkyd resins from vegetable oils

Alkyd resin is a key ingredient of all surface coating products due to their good attributes such as strength, flexibility, gloss retention, good thermal stability and low price. It can be synthesized from both edible and non-edible oil vegetable oil sources. Non-edible vegetable oil is chosen as it has no competing food uses. Bora et al. reported synthesis of alkyd resins from yellow oleander (*Thevetia peruviana*). The resin possess gratifying gloss, hardness, adhesion, chemical resistance and thermal stability which make them suitable for surface coating and binder for composite. The study reveals that yellow oleander seed oil is a good source of renewable raw material having the potential to synthesize alkyd resins for the coating industry (Bora, Gogoi, Deka, & Kakati, 2014). Bora et al. also reported the synthesis of alkyd resin from karanja (*Millettia pinnata* (L.) Panigrahi) seed oil. The karanja seed oil possesses the characteristics of a non-drying oil, for which the successful application of its alkyd resins as coating materials requires its blending with epoxy resin and epoxy hardener and curing. The physical properties of the cured epoxy-blended resin conform to the required standard for suitable application as coating material. Hence, karanja seed oil, a non-edible oil, provides a renewable sources of raw materials for production of alkyd resin, for subsequent use as coating material (Bora, Deka, Ahmed, & Kakati, 2014). Odetoeye et al. reported the preparation and evaluation of jatropha *curcas* Linneaus seed oil alkyd resin. The study reveals that

oil extracted from the seeds of *Jatropha curcas* Linneaus is a potential raw material for the coatings industry. Some properties of the alkyds compare favourably with those of the commercial standards while *Jatropha* oil alkyds exhibited outstanding colour and gloss (Odetoye, Ogunniti, & Olatunji, 2010).

Emil et al. study the characteristic and composition of *Jatropha curcas* oil seed from Malaysia. They study the psycho-chemical properties including the fatty acids of the *Jatropha* oil seed. Table 2-1 below shows the comparison of the fatty acid composition of *Jatropha curcas* oil seed, palm kernel oil, sunflower oil, soybean oil and palm oil.

Table 2-1 Fatty acid composition %

Fatty Acid	Jatropha curcas oil seed	Palm kernel oil	Sunflower oil	Soybean oil	Palm oil
Oleic 18:1	44.7	15.4	21.1	23.4	39.2
Linoleic 18:2	32.8	2.4	66.2	53.2	10.1
Palmitic 16:0	14.2	8.4	-	11.0	44.0
Stearic 18:0	7.0	2.4	4.5	4.0	4.5
Palmitoleic 16:1	0.7	-	-	-	-
Linolenic 18:3	0.2	-	-	7.8	0.4
Arachidic 20:0	0.2	0.1	0.3	-	-
Margaric 17:0	0.1	-	-	-	-
Myristic 14:0	0.1	16.3	-	0.1	1.1
Caproic 6:0	-	0.2	-	-	-
Caprylic 8:0	-	3.3	-	-	-
Lauric 12:0	-	47.8	-	-	0.2
Capric 10:0	-	3.5	-	-	-
Saturated	21.6	82.1	11.3	15.1	49.9
Monounsaturated	45.4	15.4	21.1	23.4	39.2
Polyunsaturated	33	2.4	66.2	61.0	10.5

(Edem, 2002)

Based on the comparison table of vegetable oils above, the major fatty acids in Jatropha seed oil were the oleic, linoleic, palmitic and the stearic fatty acid. Oleic acid showed the highest percentage of composition of 44.7% followed by linoleic acid with 32.8%. Thus, Jatropha seed oil can be classified as oleic–linoleic oil. Compared to others vegetable oil, Jatropha oil seed has highest oleic contain than palm oil, palm kernel, sunflower, coconut and soybean oil. This indicates the semi drying properties of Jatropha oil.

2.3 Blending of oil modified alkyd resin with the synthetic resin

Some major drawbacks of vegetable oil based alkyd resins such as low mechanical strength, low hardness, low thermal stability, and long curing time limits their practical application. To overcome these drawbacks, alkyd resins were blended with other suitable resins such as epoxy resin, amino resin, silicone resin and ketonic resin. Dutta et al. reported the preparation of alkyd/epoxy blends as multipurpose coatings. The alkyd/epoxy blends showed better performance in terms of drying time, hardness, flexibility, gloss, thermal stability and chemical resistance (Dutta, 2004). Wang et al. reported the development of alkyd/acrylic blends for the creation of hard coatings. However, alkyd resin and acrylic phase was found to be more compatible in alkyd/acrylic hybrid latex than the alkyd/acrylic blends (Wang, et al., 2010). Radicevic and Simendic reported the preparation of alkyd/melamine resin blends with various ratio of melamine. It was observed that the degree of curing alkyd/melamine resin blends increases with increasing the ratio of melamine in the blends (Radicevic & Simendic, 2005).

Blaise et al. reported preparation and characterization of blends of alkyd resin and palm oil by studying various physico-chemical properties. These properties are density, viscosity, drying time, acid value, peroxide value and dry extract. The results show that palm oil contributed to the increase of drying times of the blends; this development is attributed to the relative saturation of palm oil included in the blend. However, density and viscosity of the blends decreased as the palm oil content in the blend increased. Since the viscosity of the blend is lower compared to that of the pure alkyd, it is not likely to produce a hard film, but it may be suitable for paint systems which require low viscosity. Also, it was observed that the inclusion of palm oil led to increase in the dry extract which may also affect the thickness of alkyd resin. Contrary to the peroxide value which decrease, the acid value increase with increase of palm oil in the blend. The results suggest that palm oil can be used as a blending additive for coating formulations.

Table 2-2 Property of alkyd resin blended with different percentages of palm oil

Property	% of palm oil in the blend with alkyd resin					
	0	10	20	30	40	50
Density	0.957	0.943	0.942	0.938	0.934	0.929
Dry extract (%)	3	4	5	80	82	84
Viscosity (cps)	5000	5000	2928	1413	779	499
Drying time (h)	4	5	7	8	24	24
Gloss (%)	87.08	86.68	86.45	25.48	23.48	17.78

(Blaise, Ogunniyi, Ongoka, Moussounga, & Ouamba, 2012)

2.4 Curing behaviour of the resins

2.4.1 Curing of the blend

Edja et al. reported the synthesis, characterization, and performance characteristics of alkyd resin based on *Ricinodendron heudelotoii* oil and their blending with epoxy resins. The synthesized alkyd resins were blended with epoxy resin and methyl-ethyl ketone peroxide (MEKP) as initiator, cobalt-octoate as accelerator and poly (amido amine) as hardener. The blends were cured at room temperature and also at 50 °C. The cured resins exhibited improved performance characteristics in term of drying time at room temperature, adhesion and pencil hardness, gloss, and chemical resistance. The cured resins exhibited good tensile strength, improved elongation at break and thermally stable up to 400 °C.

Gogoi et al. reported the blends of epoxidized alkyd resins based on jatropha oil and the epoxidized oil cured with aqueous citric acid solution. To improve the performance characteristics of the resins, the resins were blended with different wt% of epoxidized jatropha oil (EJO) and aqueous citric acid solution without the addition of any other catalyst or solvent. It was observed that the properties like curing time, chemical resistance, scratch hardness, thermal stability, and tensile strength of the alkyd resins improved significantly on blending. With 50 wt% EJO content, the thermal stability and tensile strength of the blends increased. The results indicate the strong influence of the amount of EJO and citric acid on the performance of the alkyd resins.

2.4.2 Effect of nanoparticle on curing

Zabihi et al. study the curing, thermal degradation kinetics and mechanical properties of epoxy resin based on the diglycidyl ether of bisphenol A, 2,2'-Diamino-1,1'-binaphthalaene as a hardener and ZnO as a nanofiller.

Table 2-3 The result of DSC measurements of DGEBA/DABN at different level of ZnO nanoparticles at heating rate 10 K/min

Concentration of nanofiller (phr)	T _p (°C)	T _g (°C)	ΔH _{total} (J/g)	ΔH _{total} (kJ/mol)
0	109.4	74	202.83	78.53
1	105.3	84	214.64	82.34
5	102.5	93	226.34	87.07
10	107.8	88	213.73	81.87
15	115.7	79	206.56	79.59

The higher thermal and mechanical properties were obtained with a percentage of 5 phr of ZnO nanoparticles. A two-parameter (m,n) autocatalytic model (Sěsták-Berggren equation) was found to be the most adequate selected kinetic model. In addition, the predicted curves from the kinetic model fit well with dynamic DSC thermograms. The addition of ZnO nanoparticles into the epoxy matrix resulted in a significant increment in the thermal stability and activation energy of thermal degradation. The epoxy nanocomposite exhibited an increase in storage modulus and glass transition temperature compared to the neat epoxy (Omid, et al., 2011).

Pronob reported the effect of nickel oxide (NiO) nanoparticles on the performance characteristics of the Jatropha oil based alkyd and epoxy blends. The alkyd/epoxy/NiO nanocomposites showed the gradual increase in thermal stability with increasing NiO content. With 3 wt % NiO content the tensile strength of the nanocomposites indicated that the incorporation of NiO nanoparticles even in 1 wt % can greatly improves the flame retardant properties of the alkyd/epoxy/NiO nanocomposites (Pronob & Swapan, 2014).

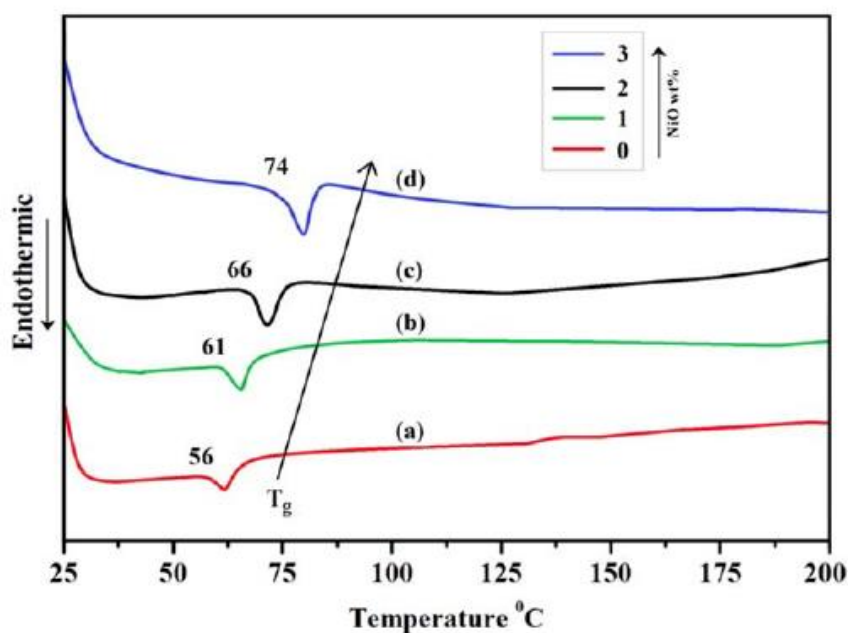


Figure 2-1 DSC traces of (a) alkyl/epoxy blend, (b) nanocomposite (1% NiO), (c) nanocomposite (2% NiO), (d) nanocomposite (3% NiO).

Based on the results of DSC traces from DSC thermograms above, the incorporation of NiO significantly improved the glass transition temperature, T_g of the nanoparticles. The T_g increases linearly with increasing NiO content and found to be increased by 20 °C for the nanocomposite with 3% NiO when compared with the neat polymer. It can be explained by the reduced mobility of the polymer chain in the presence of NiO nanoparticles. These results clearly suggest strong interaction (dipole–dipole) between NiO nanoparticles and the polymer matrix.

Table 2-4 Mechanical properties of the nanocomposite

Entry	NiO wt %	Tensile strength (MPa)	Elastic modulus (GPa)	Elongation at break (%)	Toughness	Scratch hardness (kg) ^a
1	0	17 ± 0.42	1.26 ± 0.31	67 ± 2	825	8.3
2	1	22 ± 0.13	1.81 ± 0.43	51 ± 2	880	9.4
3	2	29 ± 0.25	1.98 ± 0.16	37 ± 2	928	>10
4	3	36 ± 0.27	2.18 ± 0.18	21 ± 2	510	>10

(Pronob & Swapan, 2014)

Mechanical properties like tensile strength, elongation at break (%), Young's modulus, and toughness of the nanocomposite films are summarized in table above. Tensile strength and elastic modulus of the nanocomposites increases linearly with increasing NiO concentration. It implies the sufficient transfer of mechanical energy from polymer matrix to the nanofiller. The mechanical energy transfer is only plausible when the nanofiller is strongly attached to the polymer matrix

2.5 Summary

This chapter propose the uses of jatropha curcas oil as the main raw material to produce alkyd resin since it has highest percentage of monounsaturated oleic acid among others which indicate a semi-drying property. Since palm oil is a non-drying oil, it has low degree of unsaturation and higher degree of cross-linking through the double bonds. The blending of non-drying oil with semi-drying oil might increase the curing rate of the non-drying oil. The use of ZnO nanoparticles as the curing agent for jatropha oil based alkyd resin as it is proven to improve the thermal and mechanical properties of the nanocomposite.

3 MATERIALS AND METHODS

3.1 Overview

In general, there are three major steps to analyse the effect of ZnO nanoparticle on alkyd resins which are synthesis of ZnO nanoparticle, synthesis of alkyd resin from vegetable oil and preparation of alkyd/epoxy/ZnO nanocomposites before it is analysed by using differential scanning calorimeter (DSC).

3.2 Materials

Phthalic anhydride, glycerol, sodium hydroxide, benzoic acid and zinc nitrate tetrahydrate of analytical grade were purchased from Sigma Aldrich and used without further purification. Jatropha oil and palm oil were obtained from local supplier.

3.3 Synthesis of Zinc Oxide (ZnO) nanoparticle

ZnO nanoparticles were prepared by using sol-gel method. 0.5 M solution of zinc nitrate and a 1.0 M alkali solution of sodium hydroxide were prepared by dissolving zinc nitrate tetrahydrate $\text{Zn}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ and NaOH, respectively, in distilled water. To prepare ZnO nanoparticles, 500 mL of the alkali solution (1.0 M NaOH) was dropped at an approximate rate of 8 mL/min into a mother solution prepared by mixing 74.50 g of 0.5 M $\text{Zn}(\text{NO}_3)_2$ solution and 500.0 mL of deionized water with stirring for 12 hours. The collected product was filtered and washed several times with distilled water and dried in a vacuum oven at 100°C for several hours. The dried zinc oxide nanoparticle is then ground to fine powder using agate mortar before calcined at 300°C, 500°C, and 700°C for 2 hours in a furnace (Surabhi, Putcha, Vannka, & Gollapalli, 2013).

3.4 Synthesis of alkyd resin from the oil blend

Alkyd resin was synthesized by a two-step method from jatropha oil and palm oil (weight ratio 1:1). The first step was the alcoholysis process where monoglycerides of vegetable oil was obtained. In brief, 50g jatropha oil and 50g palm oil with 22.2g glycerol was mixed and heated to 240°C, while sodium hydroxide as catalyst (0.3 wt % with respect to oil). In the second step, the polyesterification reaction, 38.64 g of phthalic anhydride was added and the temperature was maintained at 240°C. The reaction was monitored using titration method and the reaction was stopped when the acid value dropped around 10-20 (Gogoi, Saikia, & Dolui, 2014).

Table 3-1: Composition of the ingredients to produce alkyd resins

Ingredient	Weight (g)
Jatropha oil	50
Palm oil	50
Glycerol	22.2
Sodium hydroxide (NaOH)	0.3
Phthalic anhydride	38.64

3.5 Preparation of the Alkyd/Epoxy Resin and Alkyd/Epoxy/ZnO nanocomposite

Alkyd and epoxy blends were prepared by various weight ratios of alkyd to epoxy: 0:100, 20:80, 40:60, 50:50, 60:40, 80:20 and 100:0. The alkyd/epoxy was prepared by mechanical blending. Hardener (50 wt % with respect to the epoxy resin) was added to the mixture and mechanically mixed until it is homogeneous (Gogoi, Saikia, & Dolui, 2014). The composition of the blend was presented in Table 3-2.

Table 3-2 Different ratio by mass of alkyd to epoxy resin

Resins	Alkyd (g)	Epoxy (g)	Hardener (mL)
A/E (0:100)	0	2	1
A/E (20:80)	1	4	2
A/E (40:60)	2	3	1.5
A/E (50:50)	2	2	1
A/E (60:40)	3	2	1
A/E (80:20)	8	2	1
A/E (100:0)	1	0	0

For the alkyd/epoxy/ZnO blend, similar method was adopted as above. A fixed of alkyd/epoxy (40:60) was prepared, and mixed with ZnO at different loading (0 - 8 wt %). The blend was ultrasonicated for 1.5 h to obtained homogeneous dispersion of the ZnO nanoparticles within the polymer matrix. Hardener (50 wt % with respect to the epoxy resin) was added to the mixture and mechanically mixed until it is homogeneous. The composition of the blend was presented in Table 3-3.